

# FTIR Imaging of the Microplastics Found in the Water Collected from Malir and Thatta Rivers, Sindh, Pakistan

Muneeza Salman & Tehseen Ahmed

Department of Chemistry, University of Karachi, Karachi, Pakistan

Corresponding Author email: tahmed@uok.edu.pk

## Abstract

FTIR imaging was conducted on the water of two important rivers of Sindh, Pakistan, namely Malir and Thatta. The study aims to evaluate the presence of polymer microplastics (MPs) on the surface of the water in these rivers of Sindh. The collected water was transported to the Department of Chemistry at the University of Karachi for analysis of microplastics using the oxidation method and Fourier Transform Infrared (FTIR) analysis. The results of FTIR spectroscopy, an analytical technique frequently used to detect microplastics, confirm their presence. Results showed dissimilar characteristics for both rivers, except for the 1635–1650 (amide I) and ~1530–1550 (amide II) regions, which are characteristic of polyamides (Nylon), were common. The bands at 2924 & 1460  $\text{cm}^{-1}$ , which are associated with the intense aliphatic C–H stretch and  $\text{CH}_2$  scissoring, are commonly observed in many plastics, including PP, PE, PA, PVC, and PVDF. Analysis revealed that PEHD and PTFE were the primary microplastics reported in the rivers, characterized by peaks at 2924  $\text{cm}^{-1}$  (PEHD) and 605  $\text{cm}^{-1}$  (PTFE). It was suggested that rivers contain MPs that require attention to prevent the dumping of various types of waste into river water.

**Keywords:** River water, FTIR, Microplastic, Nylon

## 1. Introduction

Plastic polymers are large synthetic molecules composed of repeating units of hydrocarbons, which are durable, lightweight, and resistant to degradation, making them widely used in packaging, textiles, and numerous other products [1,2]. However, their persistence leads to environmental accumulation, during which plastics break down into micro- and nanoplastics [2]. These particles can be ingested or inhaled by living organisms, causing physical harm, chemical toxicity, endocrine disruption, and bioaccumulation in food chains, ultimately threatening ecosystems and human health [3]. In 2010, an estimated 4.8 to 12.7 million metric tons (MMT) of plastic entered the world's oceans, with a commonly cited midpoint of approximately 8 MMT. The fact that polyethylene (PE) is the most widely produced and used polymer type in the world is one of the reasons why PE MPs are abundant in marine waters [4-9].

FT-IR spectroscopy uses the interaction of infrared (IR) light with materials to identify their chemical composition, making it particularly effective for characterizing the polymers found in microplastics. Microplastics are plastic particles smaller than 5 millimeters in size [9-12]. They originate either from the direct production of small plastic pellets (primary microplastics, e.g., microbeads in cosmetics) or from the breakdown of larger plastic debris through weathering, UV radiation, abrasion, and degradation (secondary microplastics). They may influence microbial communities, interfere with nutrient cycling, and contribute to long-term ecological imbalance. The detection, extraction, and identification of microplastics is essential to establish the presence and effect of MPs. For this purpose, Fourier Transform Infrared Spectroscopy (FTIR) is an influential analytical technique for detecting constituents by examining Infrared Absorption Spectra (IAS) [13-18]. The method has been used in microplastic identification since the turn of the century. Some essential properties of the marine samples were determined using FTIR and Scanning Electron Microscopy (SEM). It was discovered that FTIR is a valuable tool for identifying and characterizing microplastics and differentiating between polymers. Since then, FTIR has become one of the most commonly used techniques for detecting microplastics in environmental samples. Yang et al. [19] reported that  $\mu$ -FTIR spectroscopy proved effective and reliable for detecting microplastics and can be applied to assess the removal efficiency of conventional and membrane treatment processes across different water treatment plants [19].


Shim et al. reported [20] that among the present analytical methods, micro-Fourier Transform Infrared ( $\mu$ -FTIR) spectroscopy is an advanced technique for analyzing MPs, as it is a non-destructive method that can produce infrared absorption spectra for both thick and opaque materials. Generally, sample pretreatment is necessary to prevent the setup of microplastics by organic and inorganic materials and to facilitate their precise identification after digestion. The standard digestion protocols include oxidation, alkaline or acidic treatment,

and enzymatic degradation [21,22]. Fenton reagent and  $H_2O_2$  are the most used chemicals for oxidative digestion, which have no or very few effects on microplastic properties [23]. According to Prata et al. [24], 95% of 20 sediment studies used  $H_2O_2$  and/or Fenton reagent for digestion, and more than 60% of 20 studies of water samples (mainly seawater and freshwater) used  $H_2O_2$  for digestion. Enzymatic digestion is a rapid reaction for the complete degradation of organics, although it is considered an expensive, complex, and sometimes destructive method for MP extraction. The rivers in the Malir and Thatta region likely receive microplastics and other waste from various land-based sources, including urban wastewater, storm runoff carrying plastic litter, industrial discharges, and agricultural activities. The decomposition of larger plastic waste, the shedding of microfibers from synthetic textiles during washing, and waste from poorly managed landfills also contribute significantly to the pollution of these river systems. This preliminary study, conducted in the rivers of Sindh, Pakistan, aims to address the persistent problem in these river regions, which ultimately flow into the Arabian Sea. This study examines microplastics, opening the door for future studies to investigate their origin, abundance, and distribution in the region's running streams and marine food.

## 2.0. Materials and Methods

### 2.1 Sampling sites


The two sampling sites, Malir and the Thatta River (Fig. 1), were selected to investigate microplastics in these water bodies. The Malir River is a seasonal river located in Karachi, Sindh, Pakistan. It passes through the city of Karachi from the northeast, through the center, and drains into the Arabian Sea [25]. The "Thatta River" refers to the Indus River as it flows near and through the historic city of Thatta, Pakistan [26].

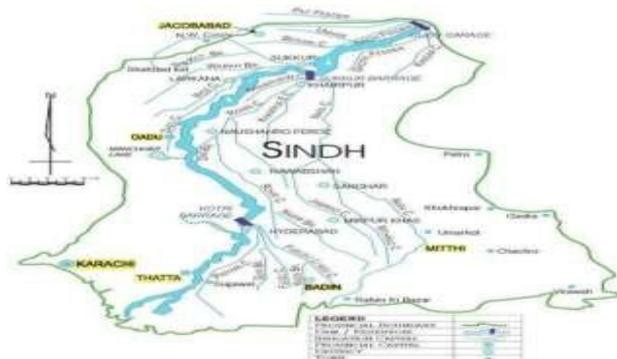

**Figure (1): Location of Rivers in Sindh, Pakistan Region**

### 2.1. Sampling

Three sampling areas of both rivers namely the Malir and Thatta River were selected for collecting samples of surface water in 1000 mL bottles dated May 4th to 7th, 2024 for the extraction of microplastics. The bottles were coated with PTFE, a hydrophobic, inert material, also known as Polytetrafluoroethylene, a synthetic, non-stick polymer famous for its high chemical resistance, low friction, and excellent heat resistance. The samples were transported to the Department of Chemistry at the University of Karachi for analysis (Fig. 2). Aquatic life and sediments were not analysed in the first phase of sampling to assess the impact of MPs on running streams.

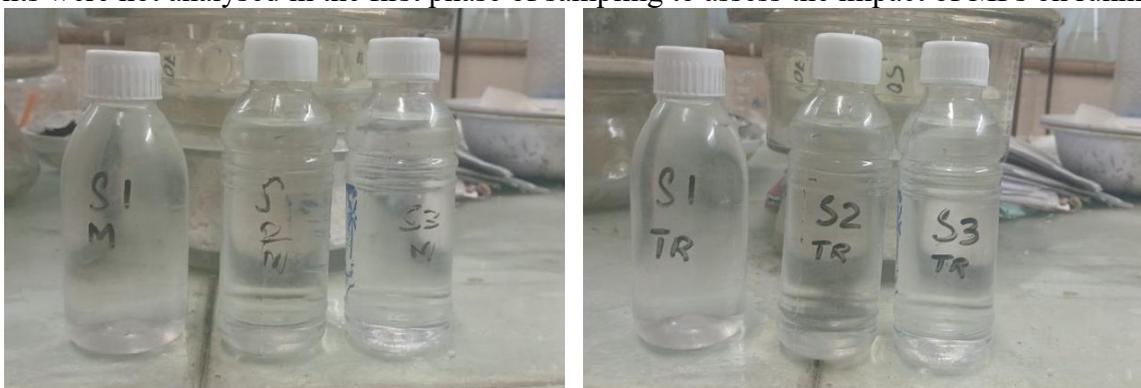

**Figure (2): The collected water sample from the rivers in Sindh, Pakistan Region**


### 2.2. Sample Preparation and FTIR analysis

All glassware was washed in triplicate with distilled water before use to analyze the samples, then covered to prevent airborne contamination. The pretreatment of the collected water was conducted by oxidation of the collected water through the use of 30% Hydrogen peroxide to remove the biological or organic contaminants,

and kept in the dark for 24 hr, as they may aggregate on the surface of the water due to the hydrophobic nature of the microplastic, followed by sieving and flushing with ethanol before evaporation of the ethanol [12,27]. The final concentrated plastic particle samples were suspended in ethanol, and samples with particle sizes greater than 80  $\mu\text{m}$  were deposited onto an infrared-reflective glass slide (MirrIR, Kevley Technologies) for reflection-mode FTIR imaging analysis. Particles < 80  $\mu\text{m}$  were deposited onto a Calcium Fluoride ( $\text{CaF}_2$ ) infrared-transparent window, which was then dried for subsequent analysis in transmission mode. This left the microplastic particles adhered to the slide, ready for analysis via FTIR imaging to identify and quantify microplastics in the samples. A Fourier Transform Infrared (FTIR) imaging system was used, with a spectral range of 4000–500  $\text{cm}^{-1}$ , a collection time of 3 sec, and 16 co-scans per measurement in reflection mode. All obtained spectra were compared with the FTIR spectrum database to verify polymer type [28]. We considered FTIR spectra matches against spectrum standards acceptable at 70% [27].

### 3.0. Results and Discussion

The research employs Fourier Transform Infrared Spectroscopy (FTIR) as an analytical technique, providing graphical representations (Fig. 3 & 4) and a compilation of identified compounds in the water samples in the range of 3500–400  $\text{cm}^{-1}$  (Table 1-3) to ascertain the precise type of microplastic (MPs) [28-35]. The key bands identified in FTIR imaging analysis of water collected from two rivers (Malir and Thatta) indicated the presence of microplastics. The microplastics that were identified by several bands positioned at a weak band near 3460.30  $\text{cm}^{-1}$  (Thatta) 3500  $\text{cm}^{-1}$  (Malir) also correspond to N–H/O–H [26], while Nylon typically exhibits an N–H stretch in the range of 3300–3350  $\text{cm}^{-1}$ , which is often weak/broadened when hydrated or at low concentration (Table 1&2). The band approximately  $\sim 3460 \text{ cm}^{-1}$  could be interpreted as broad bands of O–H stretching vibrations of carboxylic acid polymers, like polystyrene (PS) [29], while the band at 2924  $\text{cm}^{-1}$  (Thatta) & 2931  $\text{cm}^{-1}$  (Malir) showed aliphatic C–H (asymmetric) & asymmetric 1460  $\text{cm}^{-1}$ , which are linked to the intense aliphatic C–H stretch and  $\text{CH}_2$  scissoring, commonly found in many plastics, including polypropylene (PP), polyethylene (PE), polyamide (PA), poly vinyl chloride (PVC), and Polyvinylidene Fluoride (PVDF) [30]. Analysis revealed that Polyethylene high density (PEHD) and Polytetrafluoroethylene (PTFE) were the primary microplastics reported in the rivers, characterized by peaks at 2924  $\text{cm}^{-1}$  (PEHD) and 605  $\text{cm}^{-1}$  (PTFE). The absence of complex functional groups and a simplified  $\text{CH}_2$  pattern between 2900 and 3000  $\text{cm}^{-1}$  is observed, with asymmetric stretches at 2915  $\text{cm}^{-1}$  and symmetric stretches at 2848  $\text{cm}^{-1}$ , characteristic of polyvinyl chloride (PVC). The wave numbers 1535 & 1639  $\text{cm}^{-1}$  are distinguished as a pair, specifically 1635–1650  $\text{cm}^{-1}$  (amide I) and  $\sim 1530\text{--}1550 \text{ cm}^{-1}$  (amide II), which are characteristic of polyamides (Nylon) or could be interpreted as C–H bending vibrations of aromatic compounds [31]. The peak at 1111  $\text{cm}^{-1}$  is a strong band that could be a C–F stretch (suggesting a fluoropolymer such as PVDF) or an overlapping C–O or skeletal band from other polymers or additives [32]. Given the presence of aliphatic C–H at 2924  $\text{cm}^{-1}$ , PTFE, which lacks C–H, is unlikely. PVDF remains a possibility, as it exhibits strong bands in the 1111.00  $\text{cm}^{-1}$  (Thatta) and 1107.14  $\text{cm}^{-1}$  (Malir) (1170–1070  $\text{cm}^{-1}$ ) regions. The peak at 605.7  $\text{cm}^{-1}$  (Malir), typical for C–Cl (PVC) or aromatic C–H out-of-plane bends, is not definitive on its own, but it keeps PVC in the conversation. The spectral analysis revealed a water contribution in the wastewater, which appeared at the band, and can partly include H–O–H bending (adsorbed water), if drying reduces 1639 (Malir) & 1645.28  $\text{cm}^{-1}$  (Thatta), while 1535  $\text{cm}^{-1}$  (Thatta) and 1531.48  $\text{cm}^{-1}$  stay, which favors amide (Nylon). C–F bonds typically appear in the region 1000–1400  $\text{cm}^{-1}$ . Asymmetric stretching modes are usually found near 1100–1300  $\text{cm}^{-1}$ , often giving strong, sharp peaks because the C–F bond has a significant dipole moment. Therefore, a strong absorption at 1111  $\text{cm}^{-1}$  (Malir) and 1107.14  $\text{cm}^{-1}$  (Thatta) is consistent with C–F asymmetric stretching. C–F bonds typically appear in the region 1000–1400  $\text{cm}^{-1}$ . The spectrum most strongly suggests Nylon (polyamide), with PVDF and PVC as secondary possibilities. The spectrum exhibits C–Cl bond vibrations with an intense band in the region of 605  $\text{cm}^{-1}$  (Malir) and 586  $\text{cm}^{-1}$  (Thatta) (600 to 700  $\text{cm}^{-1}$ ), forming two peaks. The FTIR analysis of surface water from both rivers detected MPs, which may affect the survival of marine life, pose potential health risks to these organisms, and affect the use of these fish by humans.

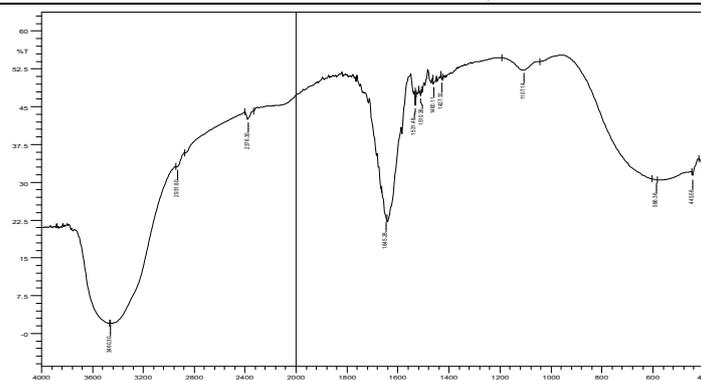

**Figure (3): FTIR Spectral Analysis of the water collected from the Thatta River**


**Table 1: Interpretation of FTIR Spectra of Thatta River**

Sample Collection Date: 04-May-2023.

Sample Description: Sample of water from the Thatta River.

Site coordinates: 24.82364 and 67.09245

Peak	Intensity	Corr. Intensity	Base (H)	Base (L)	Area	Corr. Area
445.56	31.10	1.23	447.49	420.48	12.95	0.08
586.36	30.48	0.03	603.72	584.43	9.93	0.01
1107.14	52.23	2.04	1192.01	1045.42	39.86	1.02
1427.32	50.38	0.67	1431.18	1425.40	1.70	0.02
1460.11	49.47	1.12	1463.97	1450.47	4.07	0.07
1510.26	47.12	1.26	1517.98	1506.41	3.71	0.06
1531.48	45.21	2.73	1533.41	1527.62	1.91	0.06
1645.28	22.68	0.84	1662.64	1643.35	11.68	0.26
2376.30	42.43	1.62	2401.38	2335.80	23.77	0.42
2931.80	33.08	0.53	2943.37	2872.01	33.17	0.19
3460.30	2.01	0.01	3462.22	3458.37	6.54	0.00

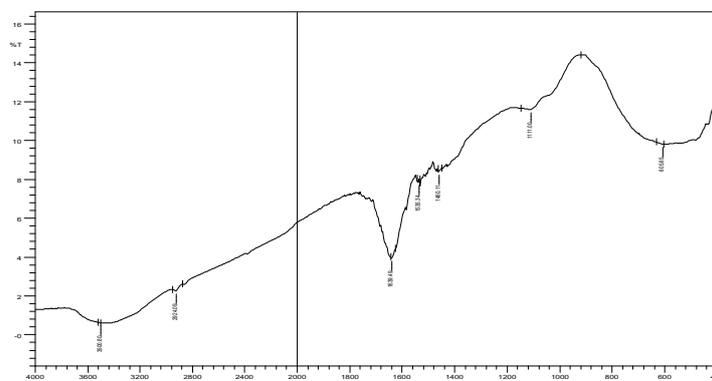

**Figure (4): FTIR Spectral Analysis of the water collected from the Malir River**

**Table 2: Interpretation of FTIR Spectra of Malir RIVER**

Sample Collection Date: 04-May-2023.

Sample Description: Wastewater-Malir River.

Sampling Site coordinates: 24.82364 and 67.09245

Peak	Intensity	Corr..Intensity	Base (H)	Base (L)	Area	Corr.Area
605.65	9.810	0.012	632.65	603.72	29.110	0.022
1111.00	11.605	0.507	1147.65	920.05	204.032	2.140
1460.11	8.399	0.173	1463.97	1450.47	14.470	0.068
1535.34	7.841	0.182	1543.05	1533.41	10.635	0.072
1639.49	3.950	0.167	1643.35	1625.99	24.079	0.226
2924.09	2.273	0.161	2949.16	2873.94	121.746	0.926
3500.80	0.622	0.003	3518.16	3498.87	42.422	0.047

Results revealed a particular Nylon variant that is frequently observed in both rivers, which may be due to the dumping of synthetic clothing and Nylon floating net cages in the vicinity. The degradation of nylon nets can be attributed to numerous environmental influences, including light intensity, temperature, and the presence of moss on the net [33-37]. The results of the present investigation are similar to those of previous studies, which

have found that the most frequent forms of MPs in sediment and water are fibers, Nylon, polymer fragments, and films. They also reported that polyethylene (PE) and polyethylene terephthalate (PET) are the most recurrent polymer types [26,31,35] (Table 3). The following summarizes how hydrodynamics affect the retention of MPs in rivers.

**Table 3: Comparative Analysis of Microplastics Found in Malir and Thatta Rivers, Sindh, Pakistan.**

Microplastic Polymer	Wavelengths (cm <sup>-1</sup> )			Band Information	
	Malir River	Thatta River	Reference Value (cm <sup>-1</sup> )		
Polymer PE, PP, PA, PVC, PTFE, PEHD and Nylon (All Polyamide) PVC	3500.80	3460	3500 [26]	N-H/O-H, (nylon)	
	2924	2931.80	2800-3000 [28]	O-H stretching/ Amine salt/Asymmetric stretching of -CH <sub>2</sub> groups	
	2924	2931.80	~2930 [28]	N-H stretching/ Asymmetric CH <sub>2</sub> stretching	
		2376.30	~2200-2400 [35]	C≡N (nitrile), C≡C (alkyne), or C=N=O (isocyanate) O=C=O	
	1639		~1635-1650 [31]	amide I polyamides (Nylon)/ C-H bending vibrations of aromatic compounds	
	1535.34	1510.26	~1530-1550 [31]	amide (Nylon)N-O stretching/(amide II)	
		1460.11			
		1427.32	1451-1492 [31]	aliphatic C-H stretch CH <sub>2</sub> bending /cellulose	
		605.65	515-690 [33]	C-Cl (PVC) or aromatic C-H/ C-Br stretch/ (PTFE)	
		445.56	400-500 [34]	M-O stretches	
		2924.09	2932	CH stretching/ (PEHD)	
		1639.49	2000-1500 [35]	C=O stretching and C=C (alkene and aromatic) stretching vibrations	
		1460.11	1645.28	1650-1850 [35]	Aromatic rings stretching
		1111.00	1107.14	1000-1400 [31]	C-F asymmetric stretching. C-F bonds

#### 4.0 Conclusion

The FTIR analysis of water collected from both rivers, Malir and Thatta, revealed the presence of microplastics, specifically Nylon, necessitating a multi-sectoral approach that involves public policies and community participation to address the entry and persistence of microplastics in the Rivers of Sindh. Based on the observed results, it is concluded that there is extensive contamination of microplastics in both river water, necessitating new research lines and further studies that examine the sources of MP emissions to accompany the present research. The observed phenomenon can be attributed to the increased diversity of plastic sources entering the river, which includes a collection of upstream debris. Ongoing monitoring and investigation into the origins of these microplastics can yield valuable insights for environmental conservation and policy development.

#### Acknowledgment

Authors express their utmost appreciation to all the teams involved in this research and acknowledge the Central Laboratory of the Department of Chemistry for the FTIR analysis.

**Author's Contribution:** Dr. Tehseen Ahmed wrote the article and supervised the research project, and Muneeza Salman conducted the research and helped in writing the article

**Conflict of Interest:** There is no conflict of interest

**Funding Resource:** NA

#### References

1. Dris, R., Gasperi, J., Rocher, V., Saad, M., Renault, N., & Tassin, B. (2015). Microplastic contamination in an urban area: a case study in Greater Paris. *Environmental Chemistry*, 12(5), 592-599. 10.1071/EN14167ff
2. Arshad, N., Alam, M. M., Su'ud, M. B. M., Imran, S., Siddiqui, T., Saleem, K., ... & Batool, A. (2023). Microplastic contamination from surface waters and commercially valuable fishes of Karachi Coast, Pakistan. *Regional Studies in Marine Science*, 62, 102955. <https://doi.org/10.1016/j.rsma.2023.102955>
3. Botterell, Z. L., Beaumont, N., Dorrington, T., Steinke, M., Thompson, R. C., & Lindeque, P. K. (2019). Bioavailability and effects of microplastics on marine zooplankton: A review. *Environmental Pollution*, 245, 98-110. <https://doi.org/10.1016/j.envpol.2018.10.065>

4. Huang, W., Song, B., Liang, J., Niu, Q., Zeng, G., Shen, M., ... & Zhang, Y. (2021). Microplastics and associated contaminants in the aquatic environment: A review on their ecotoxicological effects, trophic transfer, and potential impacts to human health. *Journal of Hazardous Materials*, 405, 124187. <https://doi.org/10.1016/j.jhazmat.2020.124187>
5. Jambeck, J. R., Geyer, R., Wilcox, C., Siegler, T. R., Perryman, M., Andrady, A., ... & Law, K. L. (2015). *Marine pollution. Plastic waste inputs from land into the ocean. Sci* 347 (6223): 768–771. DOI: [10.1126/science.1260352](https://doi.org/10.1126/science.1260352)
6. Revel, M., Châtel, A., & Mouneyrac, C. (2018). Micro (nano) plastics: a threat to human health?. *Current Opinion in Environmental Science & Health*, 1, 17-23. doi: <https://doi.org/10.1016/j.coesh.2017.10.003>.
7. Hadibarata, T., Sathishkumar, P., Prasetya, H., Pusfitasari, E. D., Tasfityati, A. N., Muzdalifah, D., ... & Sari, A. A. (2021). Microplastic contamination in the skipjack tuna (*Euthynnus affinis*) collected from the southern coast of Java, Indonesia. *Chemosphere*, 276, 130185. [10.1016/j.chemosphere.2021.130185](https://doi.org/10.1016/j.chemosphere.2021.130185).
8. Smith, M., Love, D. C., Rochman, C. M., & Neff, R. A. (2018). Microplastics in seafood and the implications for human health. *Current environmental health reports*, 5(3), 375-386., doi: [10.1007/s40572-018-0206-z](https://doi.org/10.1007/s40572-018-0206-z).
9. Ryan, P. G. (2013). A simple technique for counting marine debris at sea reveals steep litter gradients between the Straits of Malacca and the Bay of Bengal. *Marine pollution bulletin*, 69(1-2), 128-136. <https://doi.org/10.1016/j.marpolbul.2013.01.016>
10. Li, J., Green, C., Reynolds, A., Shi, H., & Rotchell, J. M. (2018). Microplastics in mussels sampled from coastal waters and supermarkets in the United Kingdom. *Environmental pollution*, 241, 35-44, <https://doi.org/10.1016/j.envpol.2018.05.038>.
11. Konechnaya, O., Luchtrath, S., Dsikowitzky, L., & Schwarzbauer, J. (2020). Optimized microplastic analysis based on size fractionation, density separation and  $\mu$ -FTIR. *Water Science and Technology*, 81(4), 834-844. <https://doi.org/10.2166/wst.2020.173>.
12. Veerasingam, S., Ranjani, M., Venkatachalapathy, R., Bagaev, A., Mukhanov, V., Litvinyuk, D., ... & Vethamony, P. (2020). Microplastics in different environmental compartments in India: Analytical methods, distribution, associated contaminants and research needs. *TrAC Trends in Analytical Chemistry*, 133, 116071., doi: [10.1016/j.trac.2020.116071](https://doi.org/10.1016/j.trac.2020.116071).
13. Kooi, M., Primpke, S., Mintenig, S. M., Lorenz, C., Gerdts, G., & Koelmans, A. A. (2021). Characterizing the multidimensionality of microplastics across environmental compartments. *Water Research*, 202, 117429. doi: [10.1016/j.watres.2021.117429](https://doi.org/10.1016/j.watres.2021.117429).
14. Olesen, K. B., van Alst, N., Simon, M., Vianello, A., Liu, F., & Vollertsen, J. (2017). Analysis of microplastics using FTIR imaging: application note. *Agilent Application Note Environment*.
15. Primpke, S., Lorenz, C., Rascher-Friesenhausen, R., & Gerdts, G. (2017). An automated approach for microplastics analysis using focal plane array (FPA) FTIR microscopy and image analysis. *Analytical Methods*, 9(9), 1499-1511.
16. Xu, J. L., Thomas, K. V., Luo, Z., & Gowen, A. A. (2019). FTIR and Raman imaging for microplastics analysis: State of the art, challenges and prospects. *TrAC Trends in Analytical Chemistry*, 119, 115629. <https://doi.org/10.1016/j.trac.2019.115629>
17. Sheriff, I., Awang, N. A., Halim, H. B., Ikechukwu, O. S., & Jusoh, A. F. (2024). Extraction and analytical methods of microplastics in wastewater treatment plants: Isolation patterns, quantification, and size characterization techniques. *Desalination and Water Treatment*, 318, 100399) ; <https://doi.org/10.1016/j.dwt.2024.100399>
18. Claessens, M., Van Cauwenberghe, L., Vandegehuchte, M. B., & Janssen, C. R. (2013). New techniques for the detection of microplastics in sediments and field collected organisms. *Marine pollution bulletin*, 70(1-2), 227-233). <https://doi.org/10.1016/j.marpolbul.2013.03.009>
19. Yang, J., Monnot, M., Sun, Y., Asia, L., Wong-Wah-Chung, P., Doumenq, P., & Moulin, P. (2023). Microplastics in different water samples (seawater, freshwater, and wastewater): Methodology approach for characterization using micro-FTIR spectroscopy. *Water Research*, 232, 119711., <https://doi.org/10.1016/j.watres.2023.119711>
20. Shim, W. J., Hong, S. H., & Eo, S. E. (2017). Identification methods in microplastic analysis: a review. *Analytical methods*, 9(9), 1384-1391, [10.1039/C6AY02558G](https://doi.org/10.1039/C6AY02558G)

21. Stock, S. R. (2019). *Microcomputed tomography: methodology and applications*. CRC press, <https://doi.org/10.1201/9780429186745>
22. Sun, J., Dai, X., Wang, Q., Van Loosdrecht, M. C., & Ni, B. J. (2019). Microplastics in wastewater treatment plants: Detection, occurrence and removal. *Water research*, *152*, 21-37., <https://doi.org/10.1016/j.watres.2018.12.050>
23. Hurley et al., 2018; Hurley, R., Woodward, J., & Rothwell, J. J. (2018). Microplastic contamination of river beds significantly reduced by catchment-wide flooding. *Nature Geoscience*, *11*(4), 251-257). <https://doi.org/10.1038/s41561-018-0080-1>
24. Prata, J. C., Da Costa, J. P., Lopes, I., Duarte, A. C., & Rocha-Santos, T. (2020). Environmental exposure to microplastics: An overview on possible human health effects. *Science of the total environment*, *702*, 134455., <https://doi.org/10.1016/j.scitotenv.2019.134455>
25. [https://en.wikipedia.org/wiki/Malir\\_River](https://en.wikipedia.org/wiki/Malir_River)],[24]
26. Thatta River, Arsalan, R. Sustainability as a Response to Climate Change Lessons Learnt from Badi.
27. Zhang, C., Wang, S., Sun, D., Pan, Z., Zhou, A., Xie, S., ... & Zou, J. (2020). Microplastic pollution in surface water from east coastal areas of Guangdong, South China and preliminary study on microplastics biomonitoring using two marine fish. *Chemosphere*, *256*, 127202. <https://doi.org/10.1016/j.chemosphere.2020.127202>.
28. Murphy, F., Ewins, C., Carbonnier, F., & Quinn, B. (2016). Wastewater treatment works (WwTW) as a source of microplastics in the aquatic environment. *Environmental science & technology*, *50*(11), 5800-5808. <https://doi.org/10.1021/acs.est.5b05416>
29. Thompson, R. C., Olsen, Y., Mitchell, R. P., Davis, A., Rowland, S. J., John, A. W., ... & Russell, A. E. (2004). Lost at sea: where is all the plastic?. *Science*, *304*(5672), 838-838. <https://doi.org/10.1126/science.1094559>
30. <https://instanano.com/all/characterization/ftir/ftir-functional-group-search/>
31. Gjeci, V., Cakaj, O., Qarri, F., Xhaxhiu, K., Lame, A., & Lazo, P. (2025). Preliminary study on FTIR analysis of microplastics in water samples of Erzeni River mouth, Adriatic Sea Albania. *Romanian Journal of Ecology & Environmental Chemistry*, *7*, 1(32-41), <https://doi.org/10.21698/rjeec.2025.103>
32. Hernández-Morales, G., López-Mendez, M. C., Rico-Barragán, A. A., Pérez-Moreno, J., Peña-Montes, C., Peralta-Pelaez, L. A., & González-Moreno, H. R. (2025). Microplastic Pollution in Tropical River: Fourier Transform Infrared Spectroscopy-Based Characterization of Abundance and Polymer Composition in Water and Sediments from Filobobos River, Mexico. *Hydrology*, *12*(5), 124. <https://doi.org/10.3390/hydrology12050124>
33. Sasivardhan, O., Interpretation of IR spectroscopy, Available from: <https://www.slideshare.net/slideshow/interpretation-of-ir-spectroscopy/66841867>
34. Yeh, M. H., & Hwang, W. S. (2006). High mechanical properties of polychloroprene/montmorillonite nanocomposites. *Material transactions*, *47*(11), 2753-2758., <https://doi.org/10.2320/matertrans.47.2753>)
35. Ali, O. How to Interpret FTIR Results: A Beginner's Guide, <https://www.azooptics.com/Article.aspx?ArticleID=2756>
36. Arat, S. A. (2024). An overview of microplastic in marine waters: Sources, abundance, characteristics and negative effects on various marine organisms. *Desalination and Water Treatment*, *317*, 100138. <https://doi.org/10.1016/j.dwt.2024.100138>
37. Annisa, N., Mahmud, M., Fatimah, A., Khotidjah, N., Riduan, R., Mahyudin, R. P., ... & Prasetia, H. (2024). Identification of microplastic types in the Martapura River's water, sediment, and fish using FTIR (Case Study: Loktangga Village and Teluk Muara Kelayan) South Kalimantan. In *E3S Web of Conferences* (Vol. 503, p. 01001). EDP Sciences. <https://doi.org/10.1051/e3sconf/202450301001>